



Adsorption Study of Highly Selective Adsorbents Obtained from Navbahor Bentonite

Mamadoliev Ikromjon Ikhomidinovich¹, Mirzakobilov Jonibek Almasovich²,
Himmatullayev Jahongir Hikmat o`g`li³

¹ Department of Medicinal Chemistry of Samarkand State Medical University.

Email: ikromjon.mamadoliev@mail.ru

² Academic Lyceum Samarkand State Medical University

³ Student of group 201 of the Faculty of Pharmacy of Samarkand State University

Abstract: Silicon adsorbents (YuKA) from navbahor bentonite of Navoi region was carried out with the participation of various organic compounds (templates) according to the "Zol-gel" technology. For this, crystals were formed by adding hexamethylenediamine and alcohol fraction as a template to liquid glass (29% SiO_2 , 9% Na_2O , 62% H_2O) $Al(NO_3)_3 \cdot 9H_2O$. After the completion of the crystallization process, the solid phase was separated from the solution using a Buchner funnel and dried in a SShU-m1 drying cabinet to 120°C and fired at 550°C in a SNOL 30/1100 muffle furnace for 8 hours to remove the template. Navbahor bentonite was crystallized for 8-9 hours and the elements and oxides content (mass, %) of Yuka samples were analyzed by X-ray fluorescence and Bentonite's derivatographic curves

Key words: Sol-gel, template, bentonite, derivatograph, silicate module, hexamethylenediamine, Crystallization, X-ray fluorescent

Introduction. In the chemical industry, adsorption methods are the most common in the purification of hydrocarbons from various mixtures and sulfur compounds, and the use of these methods allows to return to production a number of valuable compounds. Adsorbents are widely used in petrochemicals as sorbents and catalysts in the processing of oil, natural gas, and petroleum-associated gases, in the separation and purification of liquid and gaseous media [1,2]. In recent years, natural and artificial adsorbents have been widely used in the treatment of hydrocarbon raw materials [3].

Currently, one of the most important topical directions is the creation of environmentally safe sorbents, retainers and catalysts based on local raw materials [4].

Today, the world is paying great attention to the creation of waste-free or low-waste, energy and resource-efficient technologies. In successfully solving these problems, the level of purity of the substances used and produced for the technological process is important. The most important requirements for adsorbent materials are: high specific surface area, selectivity and easy regeneration. It is also necessary for the adsorbent to be cheap and harmless, to be able to maintain its adsorption properties for a long time, and to have high mechanical strength [6]. Among the sorbents used in adsorption processes and catalysis, adsorbents have a special place with acid

tolerance, thermostability and acidity properties[7]. Today, the main problem in the production of adsorbents is to reduce their cost and simplify the synthesis technology, and extensive scientific research is being conducted in this priority direction[8-10]. Today, among the technologies for purifying oil and natural gas from water vapors and sulfur compounds, adsorption processes of drying and purification using adsorbents with high absorption property at low partial pressure of mixtures, selectivity of adsorption of polar substances, etc. occupy an important place [11].

Experimental part High silica adsorbents (YuKA) were synthesized in a stainless steel autoclave at 175-200 ° C for 6-8 days according to the following method.

was prepared by adding hexamethylenediamine and alcohol fraction as a template to liquid glass (29% SiO_2 , 9% Na_2O , 62% H_2O) with rapid mixing. The value of the $Al(NO_3)_3 \cdot 9H_2O$ reaction mixture was monitored by adding a $pH 0.1 N HNO_3$ solution to it. Navbahor bentonite was added to the resulting mixture. After the completion of the crystallization process, the solid phase was separated from the solution using a Buchner funnel and dried for 12 hours in a ShSU-m1 drying cabinet at 120 ° C and fired in a SNOL 30/1100 muffle furnace at 500-550 ° C for 8 hours to remove the template.

Colloidal sol consists of macroparticles (solid dispersed phase particles).

100 g of 25% ammonium chloride was added to 10 g of adsorbents for decationization of the obtained high silicon adsorbent. The solution was kept in a water bath at 90-100 ° C with constant stirring for 2 hours, then the precipitated NH_4^+ /adsorbent was filtered, washed with distilled water, dried and calcined at 550 ° C for 8 hours. The decationized sorbent powder was then pressed into tablets and obtained as granules. Catalysts with modified adsorbents are prepared by absorbing certain salts or acids into the adsorbents.

50 hours at 115 ° C to form powdered YuKA with 100% crystallinity , at 150 ° C and about 10 hours is enough time.

In Figure 2

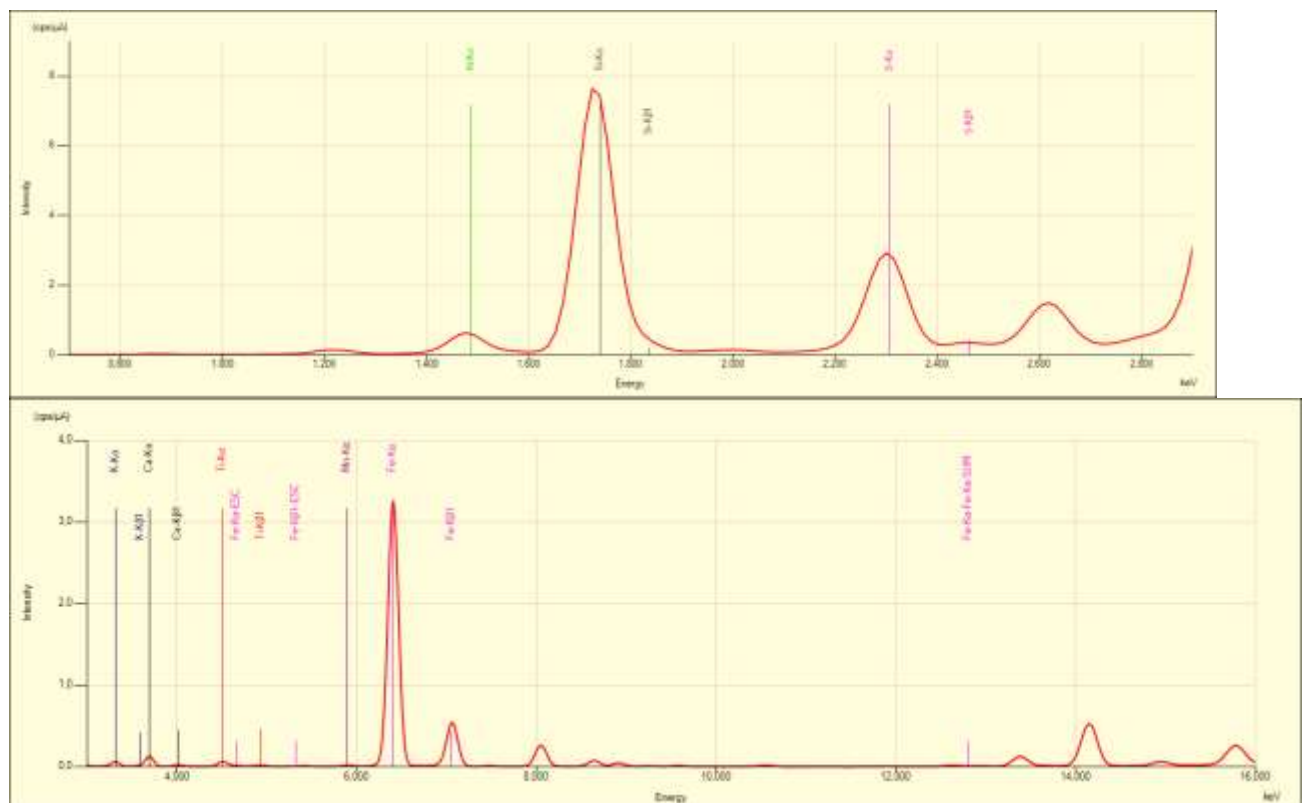


Figure 2. a) 6; b) 7 ; X-ray fluorescence results of YuKA samples obtained after crystallization for 9 hours

Figure 2 shows X-ray images of the synthesized samples after crystallization for 6.7 hours. It can be seen from the radiographs that when crystallization is carried out for 6, 7 hours, the amount of adsorbents in them is 50, 96 (respectively).

Navbahor district of bentonite chemical composition and structural characteristics are listed in Table 1.

Table 1

Name	SiO ₂	TiO ₂	Al ₂ O ₃	Fe ₂ O ₃	MgO	CaO	Na ₂ O	K ₂ O	P ₂ O ₅	SO ₃
Alkaline bentonite soil wt. %	57.91	0.35	13.69	5.10	1.84	0.48	1.53	1.75	0.43	0.75
Alkaline-earth bentonite soil wt. %	56.23	0.61	13.56	6.50	3.76	0.69	0.98	2.20	0.92	0.49

In order to study the chemical, physico-chemical and structural characteristics of bentonite, we placed 100 g of bentonite granules in a 250 cm³ glass flask and added 150 cm³ of distilled water. Flask **PE-6410** for 24 hours mixed in the device at a speed of 120. We added heated 40 ml to ground soil H_2SO_4 and heated with stirring in a water bath. After the treatment, the soil was filtered with a paper filter in a Buchner funnel and washed again with distilled water until pH=5.4-5.7. Bentonite together with filter paper was dried in a drying cabinet at 120°C for 5 hours.

Table 2

Acidic from activation then , sample mass %:

Name	SiO ₂	TiO ₂	Al ₂ O ₃	Fe ₂ O ₃	MgO	CaO	Na ₂ O	K ₂ O	MnO
Alkaline, Alkaline-earth bentonite soil mass. %	70.17	1.63	9.49	1.39	0.64	0.20	0.17	1.27	0.01

2 - As can be seen from the table, the silicate modulus of the bentonite sample by acid treatment is 7 : 1 increased to go to fight can _

The analysis of bentonite derivatographic curves was carried out (Fig. 3) shows that TG thermal logarithmic gravimeter lines are depicted, it is noted that the decrease in the mass of bentonite in the initial definite time interval over a certain period of time, DTG - differential thermal gravimeter temperature curves are depicted.

The resulting derivativeogram is presented in the figure, which consists of 4 curves. Analysis of the dynamic thermogravimetric analysis (DTGA) curve (Curve 2) shows that the DTGA curve mainly occurs in the 2 intensive decomposition temperature ranges. The 1st decomposing interval corresponds to the temperature of 106-294 °C , and the 2nd decomposing interval corresponds to the temperature of 302-950 °C.

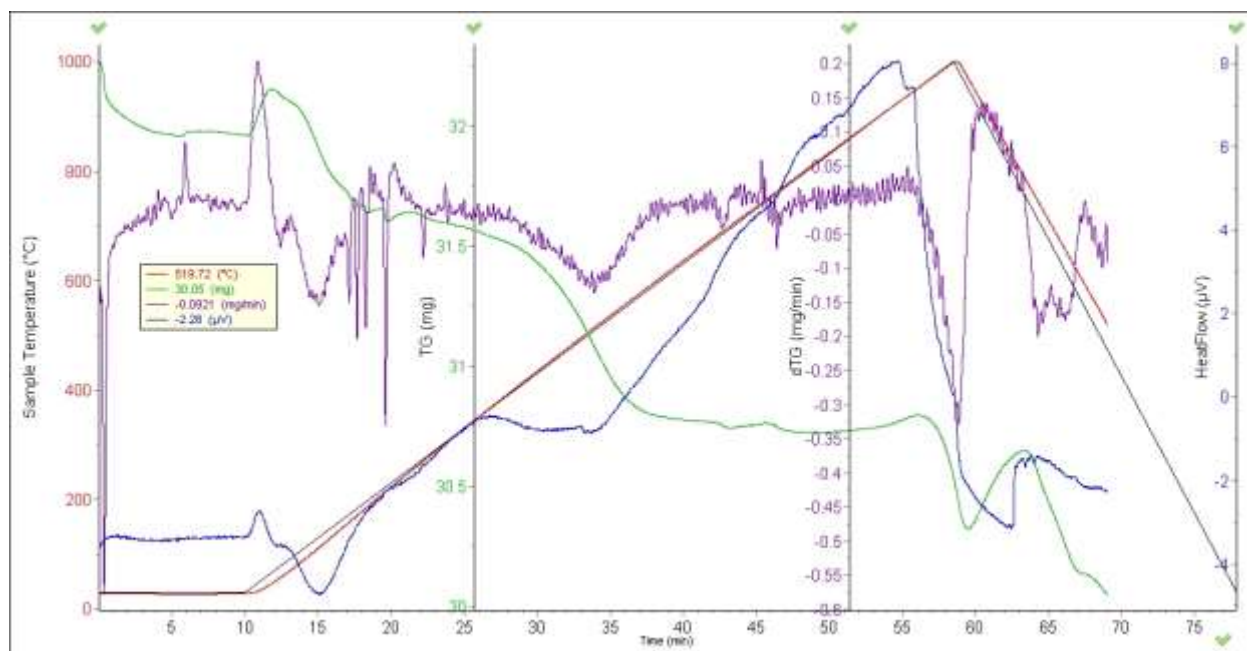


Figure 3. Activated bentonite derivativeogram

1-Temperature curve; 2- dynamic thermogravimetric analysis curve line (DTGA); 3- dynamic thermogravimetric analysis curve derivative (DTGP); 4-DSK curve.

Analysis shows that intensive decay occurs in the 2nd decay interval. In this interval, the amount of decomposition, i.e. 5.8% of the decomposition takes place.

detailed analysis of the dynamic thermogravimetric analysis curve and DSK curve is given in Table 3 below.

Table 3

Bentonite is active Analysis of DTGA and DSK curve results

No	Temperature , °C	Mass loss, %	of substance decay speed , mg/min	Amount of energy consumed ($\mu V * s / mg$))
1	50	0.225	0.136	1.46
2	100	0.885	0.555	2.54
3	200	1,055	0.653	2.21
4	300	1,135	0.487	3.22
5	400	1,685	1,147	2.02
6	500	2,069	0.455	3.03
7	600	1,815	1,499	1.65
8	700	1,521	2,156	1.21
9	800	1,812	1,244	1.77
10	900	1,958	2,622	2.02
11	1000	2,041	1,235	2.25

This derivatograph As a result of these efforts, it appears that the main mass loss takes place in the range of 160-912 ° C, in which 7.25% of the main mass, i.e. 3.21 mg of the mass, is lost.

Bentonites are small crystals of medium weight and powder with a scattering index. According to the adsorbent description, bentonite is an adsorbent consisting of a combination of meso-macro-microporosity, where mesopores make up the majority. Since the specific surface area is an average description of the internal pore size, its high value is determined by the average pore size, which is 4.9 nm for bentonite clays. [176; 24. - p. 57-61] . In conclusion, the swelling, colloidal, sorption ability of Navbahor bentonite to water and petroleum gases was studied.

Conclusions. Navbahor bentonite was obtained from clay soil, chemically treated, and high silicon adsorbents (YuKA) were prepared. A number of technological processes were implemented for the preparation of YuKA.

High silicon adsorbents were synthesized in a stainless steel autoclave at 175-200°C for 6 days according to the following method.

was prepared by adding hexamethylenediamine and alcohol fraction as a template to liquid glass (29% SiO_2 , 9% Na_2O , 62% H_2O) with rapid mixing. $Al(NO_3)_3 \cdot 9H_2O$ After the process was completed, the solid phase was separated from the solution using a Buchner funnel and dried at 120°C for 12 hours and calcined at 500-550°C for 8 hours to remove the template.

For decationization of the high silica adsorbent obtained, it was treated by adding 25% ammonium chloride and washed several times in distilled water, then calcined at 550-600°C for 8 hours. The decationized adsorbent powder was then pressed into tablets and granulated.

The chemical composition of synthesized YuKA samples, mass %, changes upon heating and structural characteristics of adsorbents (total specific surface area and volume of pores, surface-surface area corresponding to micro- and mesopores, size, crystallization conditions and physico-chemical properties of the samples) were studied based on the table information is provided.

REFERENCES

1. Lutoev A. A., Smirnov Yu. G., Ivenina I. V. Izvlechenie emulgirovannykh primesey nefi iz vody pri pomoshchi vysokodispersnykh chastits magnetite //Zashchita okrujayushchey sredy v neftegazovom komplexe. – 2014. – no. 4. – S. 40-45.
2. Serykh A. I. Forming, nature and physical and chemical properties of cationic centers and catalytic systems of vysokokremnezemnykh bases adsorbents // Izv . diss . doc. - 2014. - S. 6.
3. Kopylov A. Yu. i dr. Sovremennyejdokofaznye metody seroochistki gasovogo srya //Izvestiya vysshikh uchebnykh zavedanii. Chemistry and chemical technology. - 2010. - T. 53. – no. 9. - S. 4-8.
4. Fayzullayev, N. I. (2019). Kinetics and mechanism of the reaction of the catalytic oxycondensation reaction of methane. *Austrian Journal of Technical and Natural Sciences*, (5-6), 62-68.
5. Mamadoliyev, I. (2020). Synthesis of high-silicone zeolites. *Збірник наукових праць АГОС*, 16-20.
6. Mamadoliyev, I. I., Khalikov, K. M., & Fayzullaev, N. I. (2020). Synthesis of high silicon of zeolites and their sorption properties. *International Journal of Control and Automation*, 13(2), 703-709.
7. Mamadoliyev, I. I., & Fayzullaev, N. I. (2020). Optimization of the activation conditions of high silicon zeolite. *International Journal of Advanced Science and Technology*, 29(3), 6807-6813.

8. Fayzullaev, N. I., Mamadoliev, I. I., & Pardaeva, S. B. (2020). Research Of Sorption Properties Of High Silicon Zeolites From Bentonite. *ACADEMICIA: An International Multidisciplinary Research Journal*, 10(10).
9. Fayzullaev, N., Saginaev, A., Shukurov, B., Holliev, Sh. (2020). Cataliticheskaya dehydroaromatization neftyannogo poputnogo gas _ Zb í rnik scientist prats LÓ GO S, 122-126 .
10. Ilkhomidinovich, M. I. (2019). Study of the sorption and textural properties of bentonite and kaolin. *Austrian Journal of Technical and Natural Sciences*, (11-12), 33-37.
11. Fayzullaev N.I., Mamadoliev I.I. Optimizing the conditional activation of adsorbents with vysokim sodержaniem silicon. *Scientific journal SamGU* (2019) 3 (115) 8-12
12. Ilkhomidinovich, M. I., & Ogli, M. D. J. (2022). Change of physico-chemical properties by mechanical activation of zeolites. *ACADEMICIA: An International Multidisciplinary Research Journal*, 12(3), 10-16.
13. Ikromjon, M., Davlatjon, O., & Normurot, F. (2022). OBTAINING HIGH-SILICON ZEOLITES FROM KAOLIN. *Universum: технические науки*, (6-8 (99)), 15-19.
14. Mamadoliev, I. (2022). STUDY OF TEXTURE CHARACTERISTICS OF UNMODIFIED AND MODIFIED BENTONITE. *Химическая технология*, 36(2), 95.
15. Ikromjon, M. (2022). STUDY OF TEXTURE CHARACTERISTICS OF UNMODIFIED AND MODIFIED BENTONITE. *Universum: технические науки*, (2-7 (95)), 47-50.
16. Mamadoliev, I., Fayzullaev, N., & Baykulov, A. (2020). PRODUCTION OF HIGH-SILICON ZEOLITES FROM KAOLIN. *Збірник наукових праць ЛОГОΣ*, 21-28.
17. Patra, I., Madjeed Kammoud, K., Haleem Al-qaim, Z., Mamadoliev, I. I., Abed Jawad, M., Hammid, A. T., ... & Yasin, G. (2022). Perspectives and Trends in Advanced MXenes-Based Optical Biosensors for the Recognition of Food Contaminants. *Critical Reviews in Analytical Chemistry*, 1-20.
18. Мамадолиев, И. И., Файзуллаев, Н. И., & Юсупова, С. С. (2021). Текстурные свойства высококремниевых цеолитов полученных из навбахорского бентонита. *Universum: химия и биология*, (10-2 (88)), 61-66.
19. Ibodullaevich, F. N., Ilkhomidinovich, M. I., Bo'riyevna, P. S., & Qizi, B. M. N. (2021). Synthesis Of High Silicon Zeolites From Kaolin And Bentonite. *The American Journal of Interdisciplinary Innovations Research*, 3(03), 30-36.
20. Fayzullaev, N. I., & Mamadoliev, I. I. (2019). Yuqori kremniyli seolitning faollanish sharoitini maqbullashtirish. *SamDU ilmiy axborotnoma*, 3(115), 8-12.
21. Ilkhomidinovich, M. I. (2019). Study of the sorption and textural properties of bentonite and kaolin. *Austrian Journal of Technical and Natural Sciences*, (11-12), 33-37.
22. Mamadoliev, I. I., & Fayzullaev, N. I. (2020). Optimization of the activation conditions of high silicon zeolite. *International Journal of Advanced Science and Technology*, 29(3), 6807-6813.
23. Mamadoliev, I. I., Khalikov, K. M., & Fayzullaev, N. I. (2020). Synthesis of high silicon of zeolites and their sorption properties. *International Journal of Control and Automation*, 13(2), 703-709.
24. Umbarov, I., Turaev, K., & Samadiy, M. (2020). Research chemical composition of samples of underground salt waters of Surkhandarya and Urtabulok of Bukhara-Karshi depression. *Journal of Critikal Reviews*, 7(19), 8559-8562.

25. Умбаров, И. А. (2016, November). Комплексная переработка природных подземных вод. In Горно-металлургический комплекс: достижения, проблемы и перспективы инновационного развития: Тез. докл. Республ. науч.-техн. конф.–Навои (р. 366).
26. Умбаров, И. А. (2002). Исследование и усовершенствование технологии получения йода из йодсодержащих подземных вод. Ташкент-2002.-24 с.
27. Умбаров, И. А., & Тураев, Х. Х. (2015). Исследование процесса осаждения йода из раствора абсорбента с потенциометрическим титрованием. Вестник ТашГТУ, (4), 151-156.
28. Умбаров, И. А., & Тураев, Х. Х. (2015). Исследование кинетики окисления йодид-ионов в гидротермальных водах различными окислителями. Узбекский химический журнал, (6), 12-16.
29. Umbarov, I. A., Mamatraimov, A., & Himmatov, S. (2014). Study of Iodine Distribution in Natural Sources. In Actual Problems in Analytical Chemistry, Abstract, Proceedings of 4th Republican Research-to-Practice Conference, Termez (pp. 345-346).
30. Умбаров, И. А., Кулматов, Р. А., Тураев, Н. Й., & Ишанходжаев, С. (2000). Содержание и форма нахождения йода в подземных соленых водах Сурхандарьинской области. Узб. хим. жур, (1), 70-72.
31. Ishanhojaev, S., Umbarov, I., Kulmatov, R. A., & Mingturaev, M. (2000). Study of iodine of ions of oxidation by potentiometric method. UZBEKSKII KHIMICHESKII ZHURNAL, (6), 14-15.
32. Umbarov, I. Study of iodine of ions of oxidation by potentiometric method. vol. 5 (2021). 2021-06.01.
33. Эшкароев, С. Ч., Тураев, Х. Х., & Умбаров, И. А. (2020). Радиометрическое определение активности бета-излучений стронция-90 в почвах Сурхандарьинской области Узбекистана. In Вестник научных конференций (No. 6-1, pp. 121-124). ООО Консалтинговая компания Юком.
34. Эшмуродов, Х. Э., Гелдиев, Ю. А., Тураев, Х. Х., Умбаров, И. А., Джалилов, А. Т., & Бабамуратов, Б. Э. (2020). Получение и исследование модифицированных глифталевых смол с кремнийорганическим соединением. Universum: технические науки, (12-5 (81)), 4-8.
35. Умбаров, И. А., Тураев, Х. Х., Набиев, Д. А., Тураханов, М. И., & Холтураев, К. Б. (2019). Процессы выделений йода из концентратов. Universum: технические науки, (10-2 (67)), 48-51.
36. Умбаров, И. А., Тураев, Х. Х., Аликулов, Р. В., Чориев, О. Э., & Эшмуродов, Х. Э. (2018). Кинетика окисления йодид-ионов в присутствии различных окислителей из подземных соленых вод. Universum: технические науки, (3 (48)), 41-44.
37. Умбаров, И. А., Тураев, Х. Х., Касимов, Ш. А., & Умбарова, М. И. (2017). Усовершенствование способа выделения элементного йода из абсорбентов. ILMU AXBOROTNOMA, 5.
38. Умбаров, И. А., Тураев, Х. Х., Касимов, Ш. А., & Умбарова, М. И. УСОВЕРШЕНСТВОВАНИЕ СПОСОБА ВЫДЕЛЕНИЙ ЭЛЕМЕНТНОГО ЙОДА ИЗ КОНЦЕНТРАТОВ.
39. Курбанов, Ш. Й., Умбаров, И. А., & Бабамуратов, Б. Э. (2022). ОБЛАСТИ ПРИМЕНЕНИЯ ЙОДА И ЙОДНЫХ СОЕДИНЕНИЙ. In НАУКА И МОЛОДЁЖЬ: АКТУАЛЬНЫЕ ВОПРОСЫ СОВРЕМЕННЫХ НАУЧНЫХ ИССЛЕДОВАНИЙ (pp. 12-15).

40. Умбаров, И. А. (2021). Количественное Определение Содержания Йода В Гидротермальных Подземных Водах. CENTRAL ASIAN JOURNAL OF MEDICAL AND NATURAL SCIENCES, 2(6), 339-342.
41. Гелдиев, Ю. А., Тураев, Х. Х., Умбаров, И. А., Эшмуродов, Х. Э., & Джалилов, А. Т. (2021). СИНТЕЗ И ИССЛЕДОВАНИЕ НОВОГО СОЕДИНЕНИЯ НА ОСНОВЕ ПОЛИКРЕМНИЕВОЙ КИСЛОТЫ, МОДИФИЦИРОВАННОЙ МОНОЭТАНОЛАМИНОМ. Universum: химия и биология, (10-2 (88)), 78-81.
42. Эшанкулов, Х. Н., Тураев, Х. Х., Умбаров, И. А., & Джалилов, А. Т. (2021). ОРГАНИЧЕСКИЙ ПОЛИМЕРНЫЙ СИНТЕЗ МЕТАЛЛОВ НА ОСНОВЕ АКРИЛОНИТРИЛА. Universum: технические науки, (7-3 (88)), 5-8.
43. Гелдиев, Ю. А., Тураев, Х. Х., Умбаров, И. А., & Джалилов, А. Т. (2021). СИНТЕЗ И ИК-СПЕКТРОСКОПИЧЕСКИЙ АНАЛИЗ ПРОИЗВОДНЫХ ПОЛИКРЕМНИЕВОЙ КИСЛОТЫ С МОЧЕВИНОЙ И ФОРМАЛЬДЕГИДОМ. Universum: химия и биология, (7-1), 95-98.
44. Umbarov, I. A., & Turaev, H. K. INTERNATIONAL JOURNAL OF ENGINEERING SCIENCES & RESEARCH TECHNOLOGY INVESTIGATION MECHANISMS AND KINETICS OF OXIDATION IODIDE IONS IN HYDROTHERMAL WATERS VARIOUS OXIDANTS.
45. Umbarov, I. A., & Turaev, H. K. INTERNATIONAL JOURNAL OF ENGINEERING SCIENCES & RESEARCH TECHNOLOGY STUDY OF IODINE DISTRIBUTION FORM IN AN ABSORBENT.
46. Умбаров, И. А., Тураев, Х. Х., Касимов, Ш. А., & Умбарова, М. И. (2017). Усовершенствование способа выделения элементного йода из абсорбентов. ILMU AXBOROTNOMA, 5.
47. Potaenko, K. D., Umbarov, J., Kulmatov, R. A., Turayev, N. Y., & Ishankhodjayev, S. (1999). The removal of iodine from underground salt water by the air desorption method. UZBEKSKII KHIMICHESKII ZHURNAL, (5/6), 92-94.
48. Kulmatov, R. A., Turaev, N. Y., Kenjaev, D., Tillaev, K., & Umbarov, I. (1999). Investigation of distribution and migration forms of toxic elements by complex radioactivation methods.
49. Kulmatov, R. A., Kenjaev, D. S., Umbarov, I., Tillaev, K., & Normuradov, B. (2001). The investigation of physic-chemical forms of toxic metals by activation analysis.
50. Умбаров, И. А., & Тураев, Х. Х. (2017). Потенциометрические исследования окисления ионов йода с нитрита натрия. Universum: технические науки, (12 (45)), 48-50.
51. Умбаров, И. А., & Тураев, Х. Х. (2017). КОМПЛЕКСНАЯ ПЕРЕРАБОТКА ГИДРОТЕРМАЛЬНЫХ ВОД. In EUROPEAN RESEARCH: INNOVATION IN SCIENCE, EDUCATION AND TECHNOLOGY (pp. 8-11).
52. Умбаров, И. А., & Тураев, Х. Х. (2018). ОПРЕДЕЛЕНИЕ ЭЛЕМЕНТНОГО СОСТАВА ПОДЗЕМНЫХ СОЛЕННЫХ ГИДРОТЕРМАЛЬНЫХ ВОД. Science Time, (2 (50)), 76-79.
53. Умбаров, И. А., & Тураев, Х. Х. (2018). Подземные воды как промышленное ценное сырье. Universum: технические науки, (1 (46)), 7-9.
54. Умбаров, И. А., & Тураев, Х. Х. (2019). Изучение элементного состава гидротермальных подземных соленых вод скважины " Каттакум-2" месторождения Хаудаг. Universum: химия и биология, (9 (63)), 9-12.